

Far-infrared and submillimeter-wave conductivity in electron-doped cuprate $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$

A. Pimenov,¹ A. V. Pronin,^{1,2} A. Loidl,¹ A. Tsukada,³ and M. Naito³

¹*Experimentalphysik V, EKM, Universität Augsburg, 86135 Augsburg, Germany*

²*General Physics Institute of the Russian Acad. of Sciences, 119991 Moscow, Russia*

³*NTT Basic Research Laboratories, 3-1, Morinosato-Wakamiya, Atsugi-shi, Kanagawa 243-0198, Japan*

(Dated: February 1, 2008)

We performed far-infrared and submillimeter-wave conductivity experiments in the electron-doped cuprate $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$ with $x = 0.081$ (underdoped regime, $T_c = 25$ K). The onset of the absorption in the superconducting state is gradual in frequency and is inconsistent with the isotropic s-wave gap. Instead, a narrow quasiparticle peak is observed at zero frequency and a second peak at finite frequencies, clear fingerprints of the conductivity in a d-wave superconductor. A far-infrared conductivity peak can be attributed to $4\Delta_0$, or to $2\Delta_0 + \Delta_{\text{spin}}$, where Δ_{spin} is the resonance frequency of the spin-fluctuations. The infrared conductivity as well as the suppression of the quasiparticle scattering rate below T_c are qualitatively similar to the results in the hole-doped cuprates.

I. INTRODUCTION

The interest in the physical properties of electron-doped superconductors [1] has revived recently concerning the symmetry of the superconducting order parameter. Earlier results in these compounds on penetration depth [2], Raman [3] and tunneling spectroscopies [4] were explained in terms of conventional (s-wave) symmetry of the superconducting order parameter. However, later experiments, including half-flux effect [5], penetration-depth measurements [6], and photoemission [7] provided strong evidences for d-wave type symmetry. This contradiction can possibly be resolved on the basis of recent microwave experiments [8] and point-contact spectroscopy [9], which suggest changes of the gap symmetry as a function of doping.

Electron doping of the high- T_c cuprates can be achieved by substituting Ce^{4+} into Ln_2CuO_4 with $\text{Ln} = \text{Pr}, \text{Nd}, \text{Sm}, \text{and Eu}$ [1, 10]. Among these family $\text{Nd}_{2-x}\text{Ce}_x\text{CuO}_4$ is the earliest known and best studied compound [11]. The highest transition temperatures for electron-doped cuprates ($T_c = 30$ K) can be achieved in $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$ (LCCO) [10]. The temperature of the superconducting transition in LCCO is close to $T_c = 39$ K in a recently-discovered superconductor MgB_2 [12], which is believed to be of BCS-type [13, 14]. In order to obtain valuable information about the gap symmetry in LCCO, a direct comparison of the physical properties of these compounds can be carried out. Such analysis is provided by the low-frequency electrodynamics which directly visualizes many important features of superconductors as energy gap [15, 16] or quasiparticle scattering rate [17].

In this paper we present the far-infrared and submillimeter-wave conductivity of underdoped ($x = 0.081$, $T_c = 25$ K) LCCO thin film. In order to obtain the complex conductivity above and below the superconducting gap energy, two different experimental methods have been applied using the same sample. For frequencies below 40 cm^{-1} the complex conductivity has been obtained by the submillimeter transmission spectroscopy.

At higher frequencies the reflectance was measured using standard far-infrared techniques and the conductivity has been obtained via a Kramers-Kronig analysis of the spectra.

II. EXPERIMENTAL DETAILS

High quality $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$ film with $x = 0.081 \pm 0.01$ (underdoped regime), were deposited by molecular-beam epitaxy [10] on transparent (001) SrLaAlO_4 substrates $10 \times 10 \times 0.5 \text{ mm}^3$ in size. The thickness of the present film was 140 nm and the film revealed a sharp transition into the superconducting state ($\Delta T_c < 1$ K) at $T_c = 25$ K. Lower transition temperature compared to the optimal doping ($x \simeq 0.11$, $T_c = 30$ K [10]) confirms the underdoped character of the sample.

The transmission experiments for frequencies $5 \text{ cm}^{-1} < \nu < 40 \text{ cm}^{-1}$ were carried out in a Mach-Zehnder interferometer arrangement [19] which allows both, the measurements of the transmittance and the phase shift of a film on a substrate. The properties of the blank substrate were determined in a separate experiment. Utilizing the Fresnel optical formulas for the complex transmission coefficient of the substrate-film system, the absolute values of the complex conductivity $\sigma^* = \sigma_1 + i\sigma_2$ were determined directly from the measured spectra. In the frequency range $40 < \nu < 4000 \text{ cm}^{-1}$ reflectance measurements were performed using a Bruker IFS-113v Fourier-transform spectrometer. In addition, the reflectance for frequencies $5 < \nu < 40 \text{ cm}^{-1}$ was calculated from the complex conductivity data of the same samples, which was obtained by the submillimeter transmission. This substantially improves the quality of the subsequent Kramers-Kronig analysis of the reflectance and therefore the reliability of the data especially at low frequencies. A similar technique has been applied recently to the films of newly discovered MgB_2 [16, 20], leading to the observation of a superconducting absorption edge. Reference [16] gives

further details of the experimental set-up.

The reflectance of a thin metallic film on a dielectric substrate can be obtained from the Maxwell equations [21]:

$$r = \frac{r_{0f} + r_{fs} \exp(4\pi i n_f d / \lambda)}{1 + r_{0f} r_{fs} \exp(4\pi i n_f d / \lambda)}, \quad (1)$$

with $r_{0f} = (1 - n_f)/(1 + n_f)$ and $r_{fs} = (n_f - n_s)/(n_f + n_s)$ being the Fresnel reflection coefficients at the air-film (r_{0f}) and film-substrate (r_{fs}) interface. Here $n_f = (i\sigma^*/\varepsilon_0\omega)^{1/2}$ and n_s are the complex refractive indices of the film and substrate, respectively, λ is the radiation wavelength, d is the film thickness, $\omega = 2\pi\nu$ is the angular frequency, $\sigma^* = \sigma_1 + i\sigma_2$ is the complex conductivity of the film, and ε_0 is the permittivity of free space. Eq. (1) is written neglecting the multiple reflections from the opposite sides of the substrate.

If the film thickness is smaller than the penetration depth ($|n_f|d \ll \lambda$) and if $|n_f| \gg |n_s|$, Eq. (1) can be simplified to :

$$r \approx \frac{1 - \sigma^* d Z_0 - n_s}{1 + \sigma^* d Z_0 + n_s}, \quad (2)$$

where $Z_0 = \sqrt{\mu_0/\varepsilon_0} \simeq 377 \Omega$ is the impedance of free space. Eq. (2) provides a good approximation of the reflectance at submillimeter frequencies. For higher frequencies Eq. (1) has to be used.

III. RESULTS AND DISCUSSION

The middle panel of Fig. 1 shows the far-infrared reflectance of the underdoped LCCO film at different temperatures. A common feature of all spectra is a sharp structure above 200 cm^{-1} which is due to the phonons of the substrate (upper panel). The influence of the substrate is reduced substantially by calculating the complex conductivity via Eq. (1) but cannot be fully removed. At low frequencies and in the normally-conducting state the reflectance is approximately frequency independent. This is in agreement with Eq. (2) for a metal at low frequencies with $\sigma^* \simeq \sigma_1$. In the superconducting state, the low-frequency reflectance of the LCCO film becomes frequency dependent and follows approximately $1 - |r|^2 \propto \nu^2$. This behavior follows directly from Eq. (2): in the superconducting state the complex conductivity can be approximated by $\sigma^* \simeq i\sigma_2 \propto i/\nu$, which leads to $1 - |r|^2 \propto \nu^2$. Comparing the reflectance of LCCO in the superconducting state (Fig. 1) with the spectra of a s-wave superconductor with comparable transition temperature, e.g. with the reflectance spectra of MgB_2 (lower panel) [14, 16], significant differences can be observed. In the spectra of MgB_2 the s-wave symmetry of the superconducting order parameter leads to a sharp "knee" in the reflectance around $\hbar\nu \simeq 2\Delta_0$, which is in contrast to the spectra of LCCO where only a gradual decrease is observed. Thus, already the analysis of the

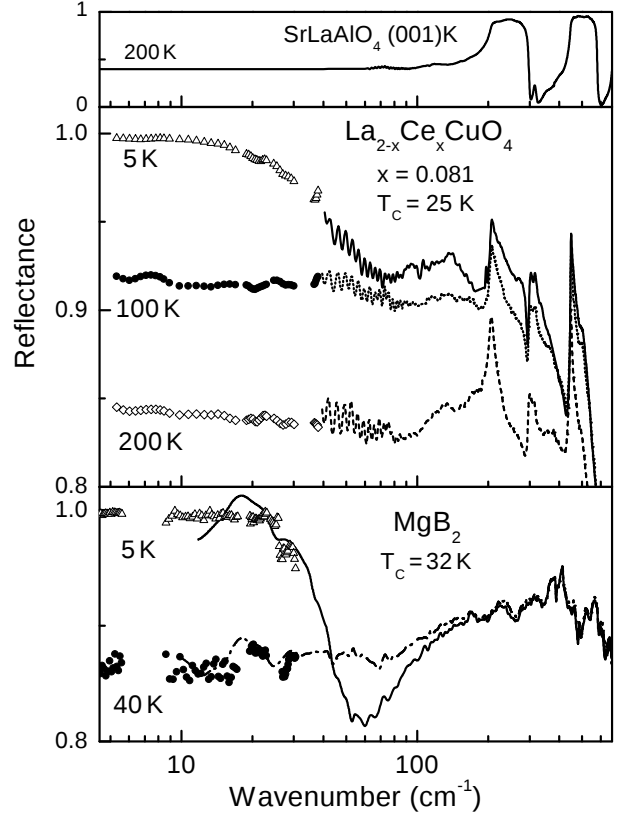


FIG. 1: Far-infrared reflectance of underdoped LCCO film at different temperatures (middle panel). Lines - directly measured data, symbols - reflectance as calculated from the complex conductivity measured by submillimeter transmission technique. Upper panel shows the reflectance of the blank substrate. Lower panel shows the reflectance of MgB_2 film [14, 16] for comparison.

reflectance spectra reveals a first indication of an unconventional gap-symmetry in LCCO.

Figure 2 shows the far-infrared conductivity of the underdoped LCCO film in the normally-conducting state. The results above 40 cm^{-1} were obtained applying the Kramers-Kronig analysis to the reflectance data and solving Eq. (1). Below 40 cm^{-1} the complex conductivity was calculated directly from the transmittance and phase shift. We recall that the resonance-like structures between 200 and 700 cm^{-1} are due to the residual influence of the substrate. In this frequency range only the overall frequency dependence of the conductivity is significant. The far-infrared conductivity in the normally-conducting state can well be described by the Drude model with a frequency-independent scattering rate $1/\tau$. At low frequencies, σ_1 is frequency-independent and σ_2 increases approximately linearly with frequency. For frequencies close to the value of the scattering rate, σ_1 starts to decrease and σ_2 shows a maximum, $\nu_{max} \simeq 1/2\pi\tau$. The gray solid line in Fig. 2 provides a good description of the conductivity at $T = 50 \text{ K}$ and demonstrates the validity of the Drude model for LCCO. Substantial devia-

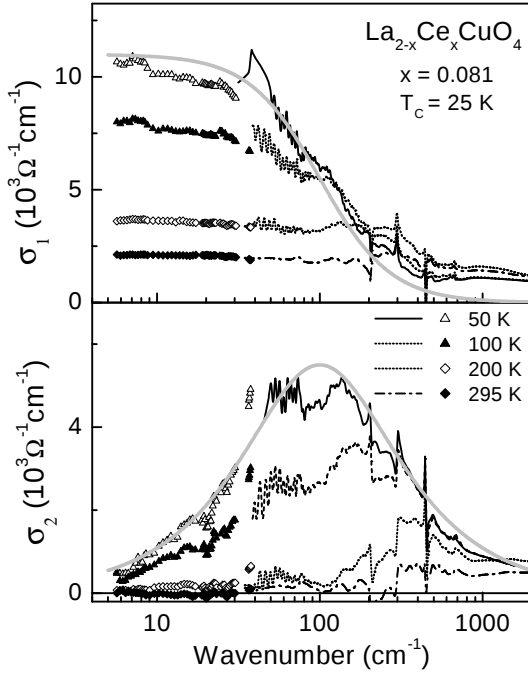


FIG. 2: Far-infrared complex conductivity of underdoped LCCO film above T_c . Upper panel - σ_1 , lower panel - σ_2 . Lines represent the conductivity obtained from the infrared reflectance, symbols - the conductivity as measured directly by the submillimeter transmission technique. Thick gray line shows the prediction of the Drude model with $1/2\pi\tau = 100 \text{ cm}^{-1}$.

tions between the data and the model can be observed above 200 cm^{-1} . These deviations can be described assuming a frequency dependence of the quasiparticle scattering, which agrees well with the infrared experiments in $(\text{NdCe})_2\text{CuO}_4$ by Homes *et al.* [22] and Singley *et al.* [23].

The infrared spectra of high- T_c cuprates and of highly anisotropic materials often show a finite-frequency peak in $\sigma_1(\omega)$. In addition to well-known mechanisms to explain the origin of this peak, like localization of the charge carriers [24], a new possibility has been proposed recently [25]. The conductivity peak at finite frequencies results from a small ($\sim 1^\circ$) tilt of the sample surface from the ideal c-axis orientation. In present experiment care has been taken to avoid such tilt effects, resulting in a peak-free real part of the infrared conductivity in the normal state.

The infrared conductivity changes dramatically upon entering the superconducting state. These data are represented in Fig. 3. The real part of the conductivity is strongly suppressed below 100 cm^{-1} (upper panel). Contrary to the conductivity of s-wave superconductors [16, 26], no clear onset of $\sigma_1(\nu)$ can be seen in the far-infrared range, which again indicates an unconventional character of the energy gap. Instead, $\sigma_1(\nu)$ clearly reveals two contributions, a Drude-like quasiparticle peak at zero frequency and a finite-frequency peak close to 100 cm^{-1} .

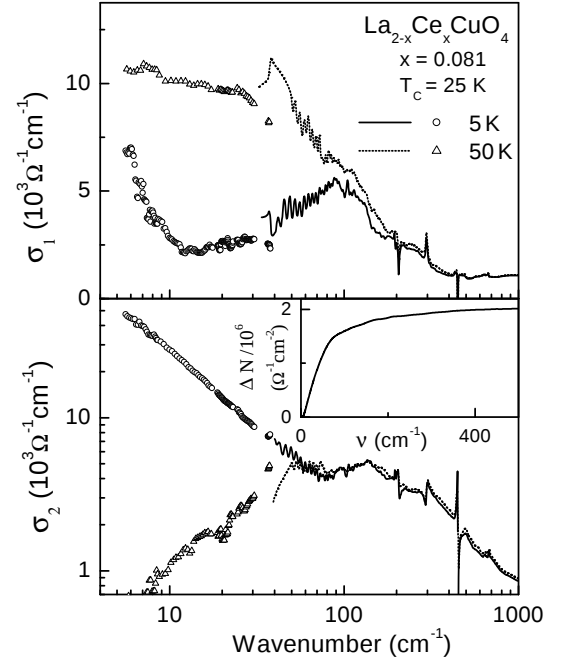


FIG. 3: Far-infrared complex conductivity of underdoped LCCO film above and below $T_c = 25 \text{ K}$. Lines represent the conductivity obtained from the infrared reflectance, symbols - the conductivity as measured directly by the submillimeter transmission technique. Inset shows the frequency dependence of the missing spectral weight, Eq. (3).

A similar maximum at correspondingly higher frequencies has been observed in infrared experiments on hole-doped cuprates [27]. Assuming a spin-fluctuation scenario of superconductivity, the frequency of the conductivity peak can be ascribed to the quadrupled frequency of the superconducting gap $4\Delta_0$ [28]. Compared to an s-wave superconductor with the conductivity onset at $2\Delta_0$, an additional shift by $2\Delta_0$ arises due to a four-particle final state. The d-wave pairing in connection with a spin-fluctuation mechanism may lead to another characteristic energy scale of the optical conductivity [29]. In that case the residual attraction in a d-wave superconductor binds a particle and a hole in a spin exciton at an energy Δ_{spin} . As a result the characteristic feature in the conductivity is shifted to $2\Delta_0 + \Delta_{spin}$ [29]. These mechanisms possibly explain the origin of the conductivity peak shown in Fig. 3. Although the optical spectroscopy is not sensitive to a sign change of the superconducting order parameter, the conductivity data in Fig. 3 provide strong experimental evidence for a highly anisotropic (and, possibly, d-wave) energy gap in underdoped LCCO: according to d-wave model calculations including spin-fluctuation scattering, a gap with nodes gives rise to a residual Drude-like peak [30], and a peak at finite frequencies resulting from inelastic scattering processes [28, 29].

Due to the suppression of the conductivity at far-infrared frequencies, substantial spectral weight is removed from this frequency range and is transferred to the

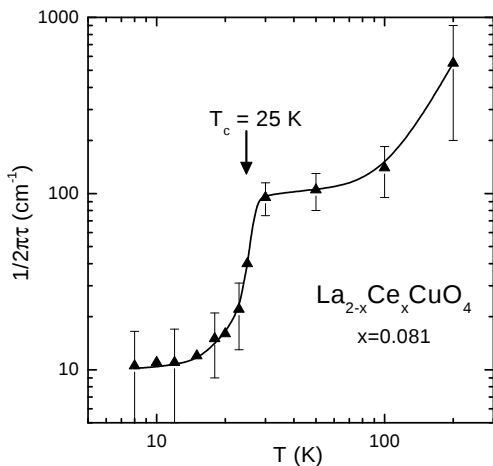


FIG. 4: Temperature dependence of the effective quasiparticle scattering in LCCO. The data have been obtained from the two-fluid analysis of the submillimeter-wave conductivity, Eq. (4).

delta-function at zero frequency (superconducting condensate). This transfer leads to the dramatic increase of $\sigma_2(\nu)$ at low frequencies, $\sigma_2(\nu) = A/\omega$. The spectral weight of the superconducting condensate can easily be obtained as the pre-factor of this proportionality $A = n_s e^2/m = 1.7 \cdot 10^6 \Omega^{-1} \text{cm}^{-2}$. The missing spectral weight (partial sum rule [31]) can be calculated by direct integration

$$\Delta N(\omega) = \frac{2}{\pi} \int_0^\omega [\sigma_{1,n} - \sigma_{1,s}](\omega) d\omega \quad . \quad (3)$$

The result is shown in the inset of Fig. 3. $A = \Delta N$ indicates the conservation of the spectral weight. The change of spectral weight, ΔN , saturates only around $\nu \sim 400 \text{ cm}^{-1}$, i.e. for frequencies well above the characteristic gap frequency. In LCCO the far-infrared saturation gives $\Delta N = 1.9 \cdot 10^6 \Omega^{-1} \text{cm}^{-2}$ and is $\sim 20\%$ higher than the measured weight of the condensate. This difference probably indicates that some amount of the spectral weight remains in the superconducting state at frequencies below the range of the present experiment.

At frequencies below 10 cm^{-1} and in the superconducting state, σ_1 shows a wing of the low-frequency excitations (upper panel of Fig. 3) which probably corresponds to a Drude-like quasiparticle peak [28, 30]. The rate of the quasiparticle scattering is strongly suppressed

compared to the normal-state ($1/2\pi\tau \simeq 100 \text{ cm}^{-1}$ at $T = 50 \text{ K}$) and attains values around 10 cm^{-1} .

Fig. 4 shows the temperature dependence of the quasiparticle scattering of LCCO. The effective scattering rate has been obtained solely from the submillimeter-wave conductivity using a two-fluid analysis [17]

$$\sigma^*(\omega) = \frac{\varepsilon_0 \omega_p^2 \tau}{1 - i\omega\tau} + A \left[\frac{\pi}{2} \delta(0) + \frac{i}{\omega} \right] \quad . \quad (4)$$

Here ω_p^2 , τ , and A represent the plasma frequency, the scattering rate of quasiparticles, and the spectral weight of the superconducting condensate. In this equation the delta function $\delta(0)$ obviously does not influence the calculations at finite frequencies and the parameter A is obtained as low-frequency limit of $\sigma_2 \cdot \omega$.

The most prominent feature of Fig. 4 is the suppression of the effective scattering rate directly at T_c . This is similar to the temperature dependence of the scattering rate in optimally-doped $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$, where a drop in $1/\tau$ has been observed, e.g. using microwave resonator technique [32] or submillimeter transmission spectroscopy [17]. However, in case of $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ the scattering rate revealed a linear temperature dependence above T_c , in contrast to LCCO where the scattering rate levels off for temperatures below $\sim 100 \text{ K}$.

IV. CONCLUSIONS

In conclusion, combining two experimental techniques we obtained the far-infrared conductivity of underdoped $\text{La}_{2-x}\text{Ce}_x\text{CuO}_4$ in the frequency range above and below the gap frequency. No characteristic onset of absorption is observed in the superconducting state, which is inconsistent with the conventional BCS scenario. At low temperatures a maximum of infrared conductivity is observed at frequencies close to 100 cm^{-1} which is qualitatively similar to the properties of the hole-doped cuprates. The quasiparticle scattering rate is suppressed upon entering the superconducting state. These results provide experimental evidence for a d-wave or highly anisotropic s-wave gap in underdoped LCCO.

V. ACKNOWLEDGEMENTS

The stimulating discussion with P. J. Hirschfeld is gratefully acknowledged. This work was supported by BMBF (13N6917/0 - EKM).

-
- [1] Y. Tokura, H. Takagi, and S. Uchida, *Nature* **337**, 345 (1989).
 - [2] D.-H. Wu, J. Mao, S. N. Mao, J. L. Peng, X. X. Xi, T. Venkatesan, R. L. Greene, and S. M. Anlage, *Phys. Rev. Lett.* **70**, 85 (1993); S. M. Anlage, D.-H. Wu, J. Mao,

- S. N. Mao, X. X. Xi, T. Venkatesan, J. L. Peng, and R. L. Greene, *Phys. Rev. B* **50**, 523 (1994); A. Andreone, A. Cassinese, A. Di Chiara, R. Vaglio, A. Gupta, and E. Sarnelli, *Phys. Rev. B* **49**, 6392 (1994); C. W. Schneider, Z. H. Barber, J. E. Evetts, S. N. Mao, X. X. Xi, and T.

- Venkatesan, *Physica C* **233**, 77 (1994).
- [3] B. Stadlober, G. Krug, R. Nemetschek, R. Hackl, J. L. Cobb, and J. T. Markert, *Phys. Rev. Lett.* **74**, 4911 (1995).
 - [4] L. Alff, S. Meyer, S. Kleefisch, U. Schoop, A. Marx, H. Sato, M. Naito, and R. Gross, *Phys. Rev. Lett.* **83**, 2644 (1999); L. Alff and R. Gross, *Superlattices Microstruct.* (UK) **25**, 1041 (1999).
 - [5] C. C. Tsuei and J. R. Kirtley, *Phys. Rev. Lett.* **85**, 182 (2000); C. C. Tsuei and J. R. Kirtley, *Rev. Mod. Phys.* **72**, 969 (2000).
 - [6] R. Prozorov, R. W. Giannetta, P. Fournier, and R. L. Greene, *Phys. Rev. Lett.* **85**, 3700 (2000); J. D. Kokales, P. Fournier, L. V. Mercaldo, V. V. Talanov, R. L. Greene, and S. M. Anlage, *Phys. Rev. Lett.* **85**, 3696 (2000).
 - [7] T. Sato, T. Kamiyama, T. Takahashi, K. Kurahashi, and K. Yamada, *Science* **291**, 1517 (2001); N. P. Armitage, D. H. Lu, D. L. Feng, C. Kim, A. Damascelli, K. M. Shen, F. Ronning, Z.-X. Shen, Y. Onose, Y. Taguchi, and Y. Tokura, *Phys. Rev. Lett.* **86**, 1126 (2001).
 - [8] J. A. Skinta, M.-S. Kim, T. R. Lemberger, T. Greibe, and M. Naito, *Phys. Rev. Lett.* **88**, 207005 (2002).
 - [9] A. Biswas, P. Fournier, M. M. Qazilbash, V. N. Smolyaninova, H. Balci, and R. L. Greene, *Phys. Rev. Lett.* **88**, 207004 (2002).
 - [10] M. Naito and M. Hepp, *Jpn. J. Appl. Phys.* **39**, L485 (2000).
 - [11] P. Fournier, E. Maiser, and R. L. Greene, in *Gap Symmetry and Fluctuations in High- T_c Superconductors*, edited by J. Bok *et al.*, (Plenum Press, NY, 1998), p.145.
 - [12] J. Nagamatsu, N. Nakagawa, T. Muranaka, Y. Zenitani, and J. Akimitsu, *Nature* **410**, 63 (2001).
 - [13] A.I. Posazhennikova, T. Dahm, K. Maki, *Europhysics Lett.* in print (cond-mat/0204272).
 - [14] A. Pimenov, *Adv. in Solid State Phys.* **42**, 267 (2002).
 - [15] A. V. Pronin, M. Dressel, A. Pimenov, A. Loidl, I. V. Roshchin and L. H. Greene, *Phys. Rev. B* **57**, 14416 (1998).
 - [16] A. Pimenov, A. Loidl and S. I. Krasnosvobodtsev, *Phys. Rev. B* **65**, 172502 (2002).
 - [17] A. Pimenov, A. Loidl, G. Jakob and H. Adrian, *Phys. Rev. B* **61**, 7039 (2000).
 - [18] M. Naito and M. Hepp, *Physica C* **357-360**, 333 (2001).
 - [19] G. V. Kozlov and A. A. Volkov in *Millimeter and Submillimeter Wave Spectroscopy of Solids*, edited by G. Grüner (Springer, Berlin, 1998), p.51.
 - [20] A. V. Pronin, A. Pimenov, A. Loidl, and S. I. Krasnosvobodtsev, *Phys. Rev. Lett.* **87**, 097003 (2001).
 - [21] O. S. Heavens, *Optical properties of thin solid films* (Dover Publ., New York, 1991).
 - [22] C. C. Homes, B. P. Clayman, J. L. Peng, and R. L. Greene, *Phys. Rev. B* **56**, 5525 (1997).
 - [23] E. J. Singley, D. N. Basov, K. Kurahashi, T. Uefuji, and K. Yamada, *Phys. Rev. B* **64**, 224503 (2001).
 - [24] D. N. Basov, B. Dabrowski, and T. Timusk, *Phys. Rev. Lett.* **81**, 2132 (1998).
 - [25] A. Pimenov, A. V. Pronin, A. Loidl, A. Tsukada, and M. Naito, cond-mat/0209218.
 - [26] L. H. Palmer and M. Tinkham, *Phys. Rev.* **165**, 588 (1968).
 - [27] J. Schützmann, W. Ose, J. Keller, K. F. Renk, B. Roas, L. Schultz, and G. Saemann-Ischenko, *Europhys. Lett.* **8**, 679 (1989); D. N. Basov, R. Liang, D. A. Bonn, W. N. Hardy, B. Dabrowski, M. Quijada, D. B. Tanner, J. P. Rice, D. M. Ginsberg, and T. Timusk, *Phys. Rev. Lett.* **74**, 598 (1995).
 - [28] S. M. Quinlan, P. J. Hirschfeld, and D. J. Scalapino, *Phys. Rev. B* **53**, 8575 (1996); S. M. Quinlan, PhD Thesis, University of California, 1994.
 - [29] A. Abanov, A. V. Chubukov, and J. Schmalian, *Phys. Rev. B* **63**, 180510(R) (2001).
 - [30] P. J. Hirschfeld, W. O. Putikka, and D. J. Scalapino, *Phys. Rev. Lett.* **71**, 3705 (1993); *Phys. Rev. B* **50**, 10250 (1994).
 - [31] D. B. Tanner and T. Timusk in *Physical Properties of high Temperature Superconductors III*, edited by D. M. Ginsberg (World Scientific, Singapore, 1992), p. 363.
 - [32] D. A. Bonn, P. Dosanjh, R. Liang, and W. N. Hardy, *Phys. Rev. Lett.* **68**, 2390 (1992); D. A. Bonn and W. N. Hardy in *Physical Properties of high Temperature Superconductors V*, edited by D. M. Ginsberg (World Scientific, Singapore, 1996). p. 7; A. Hosseini, R. Harris, S. Kamal, P. Dosanjh, J. Preston, R. Liang, W. N. Hardy, and D. A. Bonn, *Phys. Rev. B* **60**, 1349 (1999).